





# Synthesis of lead sulphide nanoparticles from egg shell membrane and its relevances

Pongayi Ponnusamy Selvi <sup>a</sup>  , T. Usharani <sup>b</sup>, B. Palanisamy <sup>c</sup>, P. Akilamudhan <sup>b</sup>, B. Sasikumar <sup>b</sup>, S. Gokila <sup>b</sup>

[Show more](#) 

 Outline |  Share  Cite

<https://doi.org/10.1016/j.dwt.2024.100098> 

[Get rights and content](#) 

Under a Creative Commons [license](#) 

*Open access*



Previous

Next



## Keywords

Egg shell; Nanoparticles; Mechano chemical method; Ultrasonic bath; Solar cell

This study innovatively repurposes eggshell waste for synthesizing lead sulphide nanoparticles, leveraging the sulphur-rich cysteine amino acid in the eggshell matrix. Three methods—mechanochemical, solvent precipitation, and ultrasonic precipitation—are employed, introducing variability through solvent choices. Comprehensive characterization demonstrates successful synthesis across all methods. Mechanochemical processing for 180min and solvent selection significantly impact nanoparticle characteristics, while the ultrasonic precipitation method, using an ultrasonic bath, proves effective. Application of these nanoparticles to a solar cell reveals enhanced performance, with voltage increasing from 9.3V to 9.7–9.9V and current rising from 354mA to 375mA. This work not only addresses waste management concerns but

contributes to sustainable semiconductor nanoparticle production for renewable energy technologies. The customizable solvent precipitation method and demonstrated solar cell improvement underscore the potential for broader applications. In conclusion, these findings indicate the feasibility of repurposing eggshell waste for sustainable materials development. The study's environmental impact is two fold, tackling waste concerns and contributing to green energy advancements. Further research may optimize synthesis conditions and explore additional applications for these eco-friendly nanoparticles.

## 1. Introduction

In the pursuit of advanced nanomaterials crucial for contemporary technological applications, our study focuses on the synthesis and theoretical characterization of lead sulfide (PbS) nanoparticles using eggshell membranes as a bio-template. As the demand for materials with enhanced dielectric and optoelectronic properties continues to grow, our investigation aims to leverage the unique properties of eggshell membranes for the controlled synthesis of PbS nanoparticles. The co-precipitation chemical synthesis route serves as the foundation for our study, building upon the bio-inspired mechanochemical synthesis technique utilizing eggshell membranes as a platform for material science [1], [2]. This approach not only aligns with sustainable practices but also exploits the inherent nano-scale characteristics of the eggshell membrane for the controlled generation of PbS nanoparticles. To comprehend the fundamental properties of PbS nanoparticles, this study utilizes X-ray diffraction (XRD) patterns [3], [4]. Scanning electron microscope (SEM) images are anticipated to reveal morphological changes, corroborating findings in the synthesis of lead sulfide nanoparticles and shedding light on the unique nanostructures formed with the eggshell membrane as a bio-template [5], [6]. Theoretical examinations of optical properties draw parallels with similar studies that explore the effects of nanoparticle size on band gaps and optoelectronic behavior [7], [8]. Dielectric characterizations are expected to demonstrate changes in various parameters, informed by previous investigations into the dielectric and electrical properties of PbS nanostructures [9]. This comprehensive study presents a theoretical exploration of the potential effects of the bio-inspired synthesis of PbS nanoparticles using eggshell membranes, offering valuable insights into their structural, optical, dielectric, and electrical properties. The anticipated enhancements underscore the promise of PbS nanoparticles synthesized through this biomimetic approach for future applications in optoelectronics [10], [11], [12].

## 2. Material and methods

In this study, eggshell waste is acquired from a local food store (Fig. 1), with a focus on preserving the delicate protein structure within the eggshell membrane (Fig. 2). The

manual removal of the membrane is meticulously undertaken to avoid compromising the integrity of the proteins through chemical treatment. The extracted membranes undergo a one-day drying process in an oven, resulting in a crisp and dry membrane subsequently finely powdered in a mortar ([Fig. 3](#)).

---



[Download:](#) [Download high-res image \(40KB\)](#)

[Download:](#) [Download full-size image](#)

Fig. 1. Collection of egg shell.

---



[Download:](#) [Download high-res image \(81KB\)](#)

[Download:](#) [Download full-size image](#)

Fig. 2. Mechanically peeled ESM.

---



[Download: Download high-res image \(36KB\)](#)

[Download: Download full-size image](#)

Fig. 3. Mortar for grinding dried ESM.

---

The milling process plays a crucial role in the synthesis of lead sulphide nanoparticles (Fig. 4). Lead acetate, a key precursor, is combined with the eggshell membrane powder in a ratio of 1:8. Given the 4% cystine content in the eggshell membrane, a substantial amount of eggshell membrane is utilized to ensure an ample supply of reactants. The milling process spans 180 min, with the first 60 min dedicated to the reduction of particle size from coarse to fine. After 120 min, sulfur atoms become available for the reaction, leading to the formation of lead sulphide nanoparticles. The synthesized nanoparticles undergo further transformation into nanofluids, a process deemed vital for subsequent evaluations. The nanofluid preparation employs an ultrasonic bath, utilizing water as a solvent, with a precisely controlled duration of one hour. This step ensures the stability and uniform dispersion of nanoparticles in the fluid medium (Fig. 5).

---



[Download: Download high-res image \(64KB\)](#)

[Download: Download full-size image](#)

Fig. 4. Ball mill.

---



[Download: Download high-res image \(98KB\)](#)

[Download: Download full-size image](#)

Fig. 5. PbS nanoparticle.

---

To assess the efficiency of the lead sulphide nanoparticles, a solar panel coating experiment is conducted (Fig. 6). The inherent semiconductor nature of lead sulphide, characterized by a small band gap, positions it favorably for optoelectronic devices. Solar panel performance is then evaluated, with the voltage increase from 9.2 to 9.6 eV being attributed to the excitation of electrons from the outer orbit of PbS molecules by incident photons containing minimal energy.

---



[Download: Download high-res image \(120KB\)](#)

[Download: Download full-size image](#)


Fig. 6. Solar panel with multimeter.

---

### 3. Results and discussion

The X-ray diffraction (XRD) analysis has elucidated compelling insights into the composition and characteristics of lead sulfide (PbS) nanoparticles within the eggshell membrane (Fig. 7 & Table 1). The XRD patterns, reflecting the crystalline structure, reveal

distinct peaks with relative intensities indicative of small crystal sizes, averaging between 5 to 10 nanometers. We compared the particle size with already published work [13], [14], [15], [16], [17], [18], [19] and showed in the [Table.2](#). This nanoscale dimension is particularly significant, as it suggests the presence of PbS nanoparticles in a quantum-confined regime, which can confer unique electronic and optical properties.

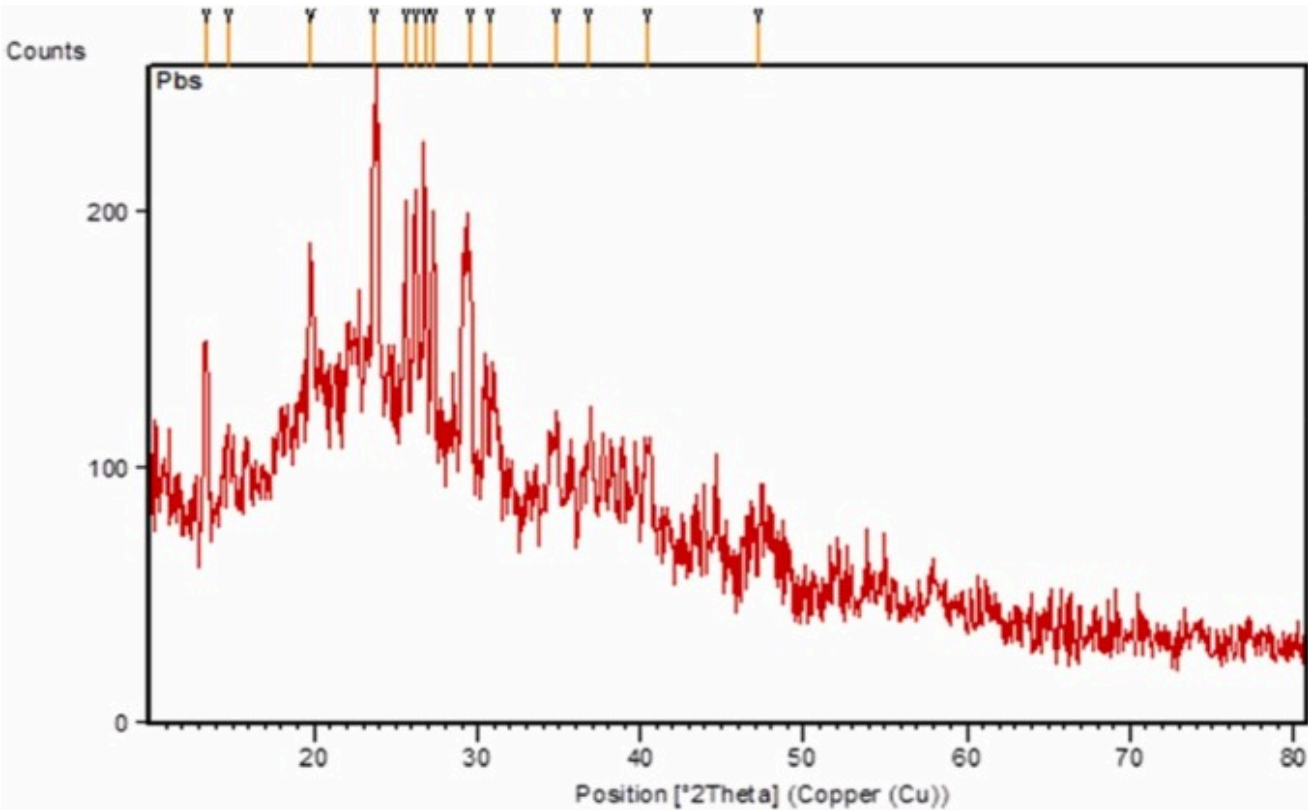

[Download: Download high-res image \(183KB\)](#)

[Download: Download full-size image](#)

Fig. 7. XRD Analysis.

Table 1. Peak list - Graphical Data.

Pos. [°2Th.]	Height [cts]	FWHM		Rel. Int. [%]
		Left [°2Th.]	d-spacing [Å]	
13.4086	100.81	0.1476	6.60357	53.66
14.7863	54.61	0.5904	5.99126	29.07
19.844	138.59	0.246	4.4742	73.78
23.6965	187.86	0.3444	3.75481	100
25.9776	151.63	0.1476	3.47875	80.72
26.2087	155.62	0.1476	3.40031	82.84
26.7659	145.89	0.1476	3.33078	77.66

Pos. [°2Th.]	Height [cts]	FWHM	d-spacing [Å]	Rel. Int.
		Left [°2Th.]		[%]
27.3305	149.39	0.1968	3.26324	79.52
29.5129	135.94	0.5904	3.02672	72.36
30.0432	66.23	0.5904	2.90557	35.26
34.8818	62.84	0.5904	2.57218	33.45
36.7908	58.89	0.3936	2.44298	31.35
40.419	58.59	0.3936	2.23167	31.19
43.0552	23.23	1.968	1.92201	12.37

Table 2. Comparison of particle size in the published work.

Author, Year of publication	Size	Analysis
Manthrammel et al., 2022	17 to 25 nm	XRD, Spectroscopy
Mohd Shkir et al., 2022	14 nm	XRD, Fourier Transform Analysis, SEM, UV-Visible Spectroscopy
Sivalingam Muthu Mariappan et al., 2022	10 – 20 nm	XRD, Raman spectroscopy
Mohd. Shkir et al., 2021	19-25 nm	XRD, SEM
Mohd. Shkir et al., 2020	20 – 40 nm	XRD, SEM, Fourier Transform Spectroscopy
Kamlesh V. Chandekar et al., 2020	13 – 15 nm	XRD, SEM, Fourier Transformation
Khan et al., 2022	Film	XRD, Raman Spectroscopy

The choice of the eggshell membrane as a template for PbS nanoparticle synthesis adds another layer of importance to these findings. The biocompatible nature of the eggshell membrane implies that it provides a conducive environment for the growth and formation of nanoparticles without inducing adverse effects. This attribute opens avenues for potential biomedical applications where the biocompatibility of materials is critical. Furthermore, the biodegradability of the eggshell membrane aligns with sustainability goals, offering an environmentally friendly template compared to synthetic



counterparts. The discussion on potential applications, particularly in solar cells and LEDs, underscores the versatility of PbS nanoparticles. The nanoscale size and unique properties of these particles make them promising candidates for enhancing the efficiency of solar energy conversion and for applications in optoelectronics.

Acknowledging the presence of impurities, such as calcium carbonate ( $\text{CaCO}_3$ ) and magnesium hydroxide ( $\text{Mg}(\text{OH})_2$ ), in the eggshell membrane before nanoparticle synthesis demonstrates a thorough understanding of the starting material. Importantly, the assurance that these impurities do not compromise the overall XRD results reinforces the robustness and reliability of the study. In conclusion, this research not only identifies the presence of PbS nanoparticles in the eggshell membrane but also sheds light on the potential of using this natural template for sustainable and cost-effective nanoparticle synthesis. The combination of biocompatibility, biodegradability, and the unique properties of PbS nanoparticles positions the eggshell membrane as a promising template for various applications, marking a significant advancement in the field of nanomaterial synthesis.

## 4. Conclusion

Lead sulphide nano particles present in the residue of the ESM matrix were successfully prepared by utilizing the ESM biomaterial and lead acetate as precursors of sulphur and lead respectively. The presence of lead sulphide nano particles was identified using XRD test. The size of nanoparticle was found between 5 to 10 nm. Confirmation of lead sulphide is also done by JCPDS card specifically available for PbS. Other methods are tried to prepare nanoparticle. Solvent precipitation was carried out by trials. Solvent such as water, ethanol and acetone were used to dissolve egg shell powder and followed by adding lead acetate. The system doesn't dissolve in anyone of the solvents. Several trials were done by adding hydrochloric acid accompanied by heating. But the system showed no response. Then the system is kept in ultrasonic bath to precipitate. The temperature was varied from 30 – 40 °C with time span of one hour. Then surfactant EDTA was added to remove the resistance between hydrophobic system and water. But the powder doesn't dissolve with variables being added. This is due to the presence of disulphide bond in cystine. Nano fluid was prepared using ultrasonic bath. Obtained nanofluid is coated over solar panel. The initial current generated without coating is 354 mA whereas current obtained after coating is 375 mA. Results shows that efficiency of the solar panel is increased. The process involving the preparation of Lead sulphide nanoparticles shows that the mechanochemical synthesis is efficient when compared with the other two methods. Mechanochemical synthesis produces nanoparticles with uniform size which is important factor in case of photo electronic devices. Thus, nanofluid is produced by using water as a solvent after undergone several trials. Results shows that the efficiency of solar panel was increased when nanofluid is coated on solar panel.




## Declaration of Competing Interest

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.




[Recommended articles](#)

## References

- [1] Chidi C. Uhuegbu  
Growth and characterization of lead sulphide thin film for solar cell fabrication  
Cana J Sci Ind Res, 2 (2011), pp. 230-241  
[Google Scholar ↗](#)
- [2] Matej Balaz, Peter Balaz, Maria J. Sayagues, Anna Zorkovska  
Bio–inspired mechanochemical synthesis of semiconductor nanomaterial using eggshell membrane  
Matrl Sci Semi Process, 16 (2013), pp. 1899-1903  
 [View PDF](#)   [View article](#)   [View in Scopus ↗](#)   [Google Scholar ↗](#)
- [3] Eggshell Matej Balaz  
membrane bio material as a platform for application in material science  
Acta Biomater, 10 (2014), pp. 3827-3843  
[Google Scholar ↗](#)
- [4] N.C. Rath, R. Liyanage, S.K. Makkar, J.O. Lay Jr  
Protein profiles of hatchery egg shell membrane, Rath et al  
Proteome Sci, 15 (2017), pp. 1-9  
[Crossref ↗](#)   [Google Scholar ↗](#)
- [5] B.Kotadiya Naresh, J.Kothari Anjana, K. Devendra Tiwari, Tapas Chaudhur  
Photoconducting nanocrystalline lead sulphide thin films obtained by chemical bath deposition  
Appl Phys A, 7 (2012), pp. 819-824  
[Google Scholar ↗](#)
- [6] P.K. Shukla, Sandeep Kumar Tomar, Bhaskar Bhattacharya, Pramod K. Singh  
Synthesis of lead sulphide nanoparticles for electrode application of dye synthezied solar cells  
Nanosci Nanotechnol Lett, 6 (2014), pp. 31-36  
[View in Scopus ↗](#)   [Google Scholar ↗](#)

- [7] Huilan Su, Jie Han, Na Wang, Qun Dong, Di Zhang, Chunfu Zhang  
In situ synthesis of lead sulfide nanoclusters on eggshell membrane fibers by an ambient bio-inspired technique, Smart Mater Struct, 17 (2008), pp. 015-045  
[Google Scholar ↗](#)
- [8] Sascha Kull, Leonard Heymann, AnaB. Hungria, Christian Klinke  
Synthesis of single-crystalline lead sulfide nanoframes and nanorings  
Chem Mater, 31 (2019), pp. 5646-5654  
[Crossref ↗](#) [View in Scopus ↗](#) [Google Scholar ↗](#)
- [9] Qi Wang, Chunlei Ma, Jianke Tang, Cuihong Zhang, Lihua Ma  
Eggshell membrane templated MnO<sub>2</sub> nanoparticles: facile synthesis and tetracycline hydrochloride decontamination  
Nanosca Res Let, 13 (2018), pp. 15-31  
[Google Scholar ↗](#)
- [10] Miao Liang, Rongxin Su, Wei Qi, Yanjun Yu  
Synthesis of well-dispersed Ag nanoparticles on eggshell membrane for catalytic reduction of 4- nitrophenol  
J Mater, Sci, 49 (2014), pp. 1639-1647  
[Crossref ↗](#) [View in Scopus ↗](#) [Google Scholar ↗](#)
- [11] Sheng-Heng Chung, Arumugam Manthiram  
Carbonized eggshell membrane as a natural polysulfide reservoir for highly reversible Li-S batteries  
Adv Mater, 26 (2014), pp. 1360-1365  
[Crossref ↗](#) [View in Scopus ↗](#) [Google Scholar ↗](#)
- [12] Parukuttyamma Sujatha Devi, Suparna Banerjee, Sebanti Roy Chowdhury, G. opinatha, Suresh Kumar  
Eggshell membrane: A natural biotemplate to synthesize fluorescent gold nanoparticles  
RSC Adv, 2 (2012), pp. 11578-11585  
[Crossref ↗](#) [View in Scopus ↗](#) [Google Scholar ↗](#)
- [13] Sivalingam Muthu Mariappan, Sung Jun Hong, Byungchan Han, Mohd Shkir, Elangovan Vinoth, Stella Mary, K. Janani, Archana, Balasubramanian Karthikeyan, Hamed Algarni, Salem AlFaify  
Slow excitonic carrier cooling in Sr-doped PbS nanocrystals hot Carr Device: Integr Exp first-Princ Approach J Mater Chem C, 10 (2023), p. 6634

[Google Scholar ↗](#)

- [14] Mohd Shkir, Kamlesh V. Chandekar, Md.Milon Hossain, Baskaran Palanivel, Nafis Ahmad, I.M. Ashraf, H.H. Somaily, H. Algarni, S. AlFaify  
Enhanced dielectric and electrical properties of PbS nanostructures  
facilely synthesized by low-cost chemical route: an effect of Ce doping  
concentrations  
Mater Chem Phys, 278 (2022), Article 125626  
 [View PDF](#) [View article](#) [View in Scopus ↗](#) [Google Scholar ↗](#)
- [15] Z.R. Khan, Mohd Shkir  
Improved opto-nonlinear and emission properties of spray pyrolysis  
grown Nd:PbS nanostructured thin films  
Phys B: Condens Matter, 627 (2022), Article 413612  
 [View PDF](#) [View article](#) [View in Scopus ↗](#) [Google Scholar ↗](#)
- [16] M. Aslam Manthrammel, Sivalingam Muthu Mariappan, Mohd Shkir, S. AlFaify  
A facile microwave assisted synthesis of La@PbS nanoparticles and their  
characterizations for optoelectronics  
J Inorg Organomet Polym Mater, 32 (2022), pp. 469-477  
[Google Scholar ↗](#)
- [17] Mohd Shkir, Baskaran Palanivel, KamleshV. Chandekar, Aslam Khan, M. Ahmed, El.Toni  
Anees, A. Ansari, Rayees Ahmad Zargar, M.A. Sayed, S. AlFaify  
Microwave-assisted synthesis of Cu doped PbS nanostructures with  
enhanced dielectric and electrical properties for optoelectronic  
applications  
Mater Sci Eng: B, 271 (2021), Article 115268  
 [View PDF](#) [View article](#) [View in Scopus ↗](#) [Google Scholar ↗](#)
- [18] Mohd. Shkir, Kamlesh V. Chandekar, T. Alshahrani, Ashwani Kumar, Aslam Khan, S. AlFaify  
An impact of La doping content on key physical properties of PbS  
spherical nanoparticles facilely synthesized via low temperature  
chemical route  
Eur Phys J, 135 (2020), p. 816  
[Google Scholar ↗](#)
- [19] Kamlesh V. Chandekar, T. Alshahrani, A. Ben Gouider Trabelsi, F.H. Alkallas  
Mohd.Shkir and S. AlFaify, Novel rare earth yttrium doping effect on  
physical properties of PbS nanostructures: facile synthesis and  
characterization  
J Mater Sci, 56 (2021), pp. 4763-4781

## Cited by (0)

© 2024 The Authors. Published by Elsevier Inc.



All content on this site: Copyright © 2025 Elsevier B.V., its licensors, and contributors. All rights are reserved, including those for text and data mining, AI training, and similar technologies. For all open access content, the relevant licensing terms apply.

